

22(21)
212 to

CANMET


REPORT 78-24

Canada Centre
for Mineral
and Energy
Technology

Centre canadien
de la technologie
des minéraux
et de l'énergie

DEVELOPMENT OF A SIMULATED CATALYST AGING TECHNIQUE

J.F. KRIZ AND M. TERNAN

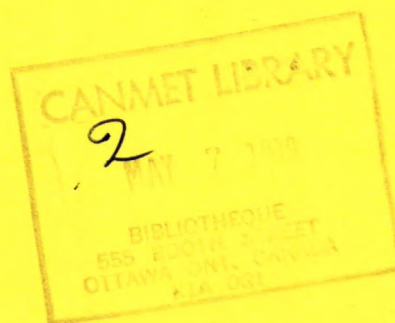

ENERGY RESEARCH PROGRAM
ENERGY RESEARCH LABORATORIES



Energy, Mines and
Resources Canada

Énergie, Mines et
Ressources Canada

JUNE 1978

© Minister of Supply and Services Canada 1978

Available by mail from:

Printing and Publishing
Supply and Services Canada,
Ottawa, Canada K1A 0S9

CANMET
Energy, Mines and Resources Canada,
555 Booth St.,
Ottawa, Canada K1A 0G1

or through your bookseller.

Catalogue No. M38-13/78-24 Price: Canada: \$1.25
ISBN 0-660-10191-2 Other countries: \$1.50

Price subject to change without notice.

© Ministre des Approvisionnements et Services Canada 1978

En vente par la poste:

Imprimerie et Édition
Approvisionnement et Services Canada,
Ottawa, Canada K1A 0S9

CANMET
Énergie, Mines et Ressources Canada,
555, rue Booth
Ottawa, Canada K1A 0G1

ou chez votre libraire.

N° de catalogue M38-13/78-24 Prix: Canada: \$1.25
ISBN 0-660-10191-2 Autres pays: \$1.50

Prix sujet à changement sans avis préalable.

DEVELOPMENT OF A SIMULATED CATALYST AGING TECHNIQUE

by

J.F. Kriz* and M. Ternan**

ABSTRACT

A technique to simulate catalyst aging was developed whereby catalyst deactivation is accelerated by changing the operating conditions. Because of greatly accelerated aging, the technique can provide preliminary information on aging rates in a much shorter time than is normally required for performing an actual aging test. This report documents a series of tests performed to investigate the effect of variations in space velocity and temperature. Suitable deactivation conditions were found to prevail when both the space velocity and temperature were increased. In one particular case, this increase accelerated the aging rate about thirty times. The relationship between the aging patterns observed under simulated and actual aging conditions is discussed. An approximate quantitative link was established which provided an estimate of the catalyst aging rate from tests performed at simulated conditions.

*Research Scientist, **Section Head, Catalysis Development Section, Synthetic Fuels Research Laboratory, Energy Research Laboratories, Canada Centre for Mineral and Energy Technology, Department of Energy, Mines and Resources, Ottawa, Canada.

LA MISE AU POINT D'UNE TECHNIQUE DE SIMULATION
DU VIEILLISSEMENT DU CATALYSEUR

par

J.F. Kriz* et M. Ternan**

RESUME

Une technique de simulation du vieillissement du catalyseur a été mise au point par laquelle la désactivation du catalyseur est accélérée en changeant les conditions de fonctionnement. Comme le vieillissement a été accéléré, cette technique peut fournir l'information préliminaire sur les taux de vieillissement plus rapidement que si les essais de vieillissement réels étaient effectués. Le présent rapport donne les précisions sur une série d'essais effectués afin d'analyser les effets de variation de la vitesse spatiale et de la température. Lorsque la vitesse spatiale et la température étaient augmentées, des conditions de désactivation adéquates étaient maintenues. Dans un cas particulier, l'augmentation de la température et de la vitesse spatiale a accéléré le vieillissement environ 30 fois. On explique le rapport qui existe entre les profils de vieillissement observés selon des conditions de simulation ou normales. Grâce aux essais effectués dans des conditions de simulation, on a pu établir un lien quantitatif approximatif qui donne un estimé du taux de vieillissement du catalyseur.

* Chercheur scientifique, **Chef de section, Section du développement des catalyseurs, Laboratoire de recherche sur les combustibles synthétiques, Laboratoire de recherche énergétique, Centre canadien de la technologie des minéraux et de l'énergie, Ministère de l'Énergie, des Mines et des Ressources, Ottawa, Canada.

CONTENTS

	<u>Page</u>
ABSTRACT	1
RESUME	ii
INTRODUCTION	1
EXPERIMENTAL EQUIPMENT AND MATERIALS	2
OPERATING CONDITIONS	2
RESULTS AND DISCUSSION	8
True Aging	8
High Space Velocity	8
Simulating Aging	10
Link Between Simulated and True Aging	14
CONCLUSIONS	15
ACKNOWLEDGEMENTS	15
REFERENCES	16

TABLES

1. Properties of Athabasca Bitumen	3
2. True Aging Run Liquid Product Specifications	7
3. High Space Velocity Run Liquid Product Specifications	9
4. Simulated Aging Run Liquid Product Specifications	13
5. Deactivation Levels for Simulated Aging Liquid Product Specifications	13

FIGURES

1. Schematic diagram of the feed section for simulated aging	3
2. Front view of feed section for simulated aging test	4
3. Specific gravity (15/15°C) and sulphur content (wt %) in the liquid product versus time on stream (h) during true aging	9
4. Specific gravity (15/15°C) and sulphur content (wt %) in the liquid product versus time on stream (h) during simulated aging	11

INTRODUCTION

In keeping with aims of the Energy Research Program of the Canada Centre for Mineral and Energy Technology (CANMET), Department of Energy, Mines and Resources and its policy of ensuring effective use of mineral and energy resources, considerable effort has been focused on processing oil sand bitumens and other residual oils. Tests have indicated that a major problem in developing a catalytic hydrocracking process is rapid deactivation of commercially available catalysts (1).

The problem of rapid catalyst fouling has been alleviated through two approaches recently investigated at CANMET. In one, a two-stage process is non-catalytic in its first stage (2) and the other uses a relatively inexpensive disposable catalyst (3). Although it is not yet certain which refining alternative will prove most economical, the availability of fouling resistant catalysts could play a decisive role in implementing catalytic hydrocracking schemes.

Under hydrocracking conditions, heavy oils produce deposits that accumulate on the catalyst surface. By poisoning and by hindering accessibility of the active sites, these deposits cause fouling of the catalyst. Material that is so deposited is either originally present in the feed, such as heavy metals and minerals, or is formed during hydrocracking, such as coke. Not all deposits deactivate the surface at the same rate. It was established by repeated regeneration that rapid fouling under typical bitumen hydrocracking conditions is caused primarily by coke formation (1). To obtain a longer-lasting formulation, catalyst development should therefore focus on types that resist coke formation. Such an effort would involve a systematic approach to catalyst production based on information obtained in aging tests.

To determine true aging characteristics, actual processing conditions must be maintained because they affect product formation and thereby also the process of deactivation. However, a serious disadvantage of aging tests under actual processing conditions is that they are slow and thus consume a great deal of time and manpower. The time involved becomes critical if aging characteristics are required for a large number of catalysts. It is the purpose of this report to describe a technique that simulates catalyst aging and provides preliminary information in a much shorter time.

EXPERIMENTAL EQUIPMENT AND MATERIALS

A bench-scale fixed-bed reaction system was used, in which the bitumen mixed with hydrogen flowed up through the catalyst bed continuously. Liquid and vapour were separated in receiver vessels. The equipment was previously described in detail (4) but the following modifications were made to accommodate the particular requirements of the present study:

1. The feed measuring device is shown in Fig. 1. Bitumen was stored in the heated hopper from which it could be fed through taps into two 1000-mL burettes in a heated plastic cabinet, a photograph of which is shown in Fig. 2. With a light positioned behind the cabinet and the inside of the cabinet heated to about 75°C, it was possible to monitor the feed level in the burettes. A Milton Roy "Constametric" pump, model number TCP 43-43 TJ, was used to feed the bitumen through heated lines into the reactor. A pressure gauge was placed at the pump outlet to monitor pressure at the pump head.
2. To reduce the reactor volume, a stainless steel insert was machined to fit it, reducing the inside diameter to 1.27 cm from 2.54 cm but maintaining length at 30.5 cm.

The catalyst selected for comparative runs was a commercial type Harshaw 0603T with 3 wt % CoO and 12 wt % MoO₃ supported on alumina in the form of cylindrical 3.2-mm pellets. About 150 g of this catalyst represented a full reactor load but only about 30 g could be loaded with the insert. The rate of aging was evaluated using Athasbasca bitumen obtained from Great Canadian Oil Sands Limited at Fort McMurray, Alberta. Properties of the feedstock are listed in Table 1.

OPERATING CONDITIONS

The conditions that affect catalyst deactivation in a continuous flow system are temperature, hydrogen pressure, hydrogen flow rate and liquid space velocity. The hydrocracking process consists of a number of complex reaction steps, initially involving various constituents of bitumen. Catalytic processes on active surface sites participate in some of the reaction steps.

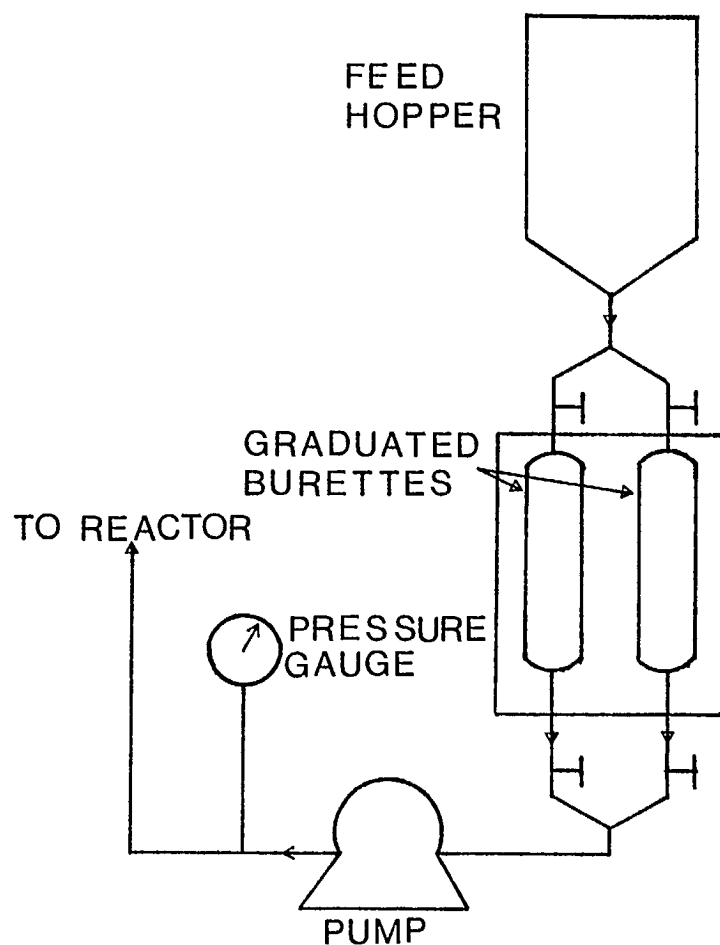


Fig. 1. Schematic diagram of the feed section for simulated aging

TABLE 1

Properties of Athabasca Bitumen

Specific gravity	1.009	(15/15°C)
Sulphur	4.48	wt%
Ash	0.59	wt%
Conradson carbon residue	13.3	wt%
Pentane insolubles	15.5	wt%
Benzene insolubles	0.72	wt%
Carbon	86.36	wt%
Hydrogen	10.52	wt%
Nitrogen	0.45	wt%
Pitch (525°C+)	51.5	wt%

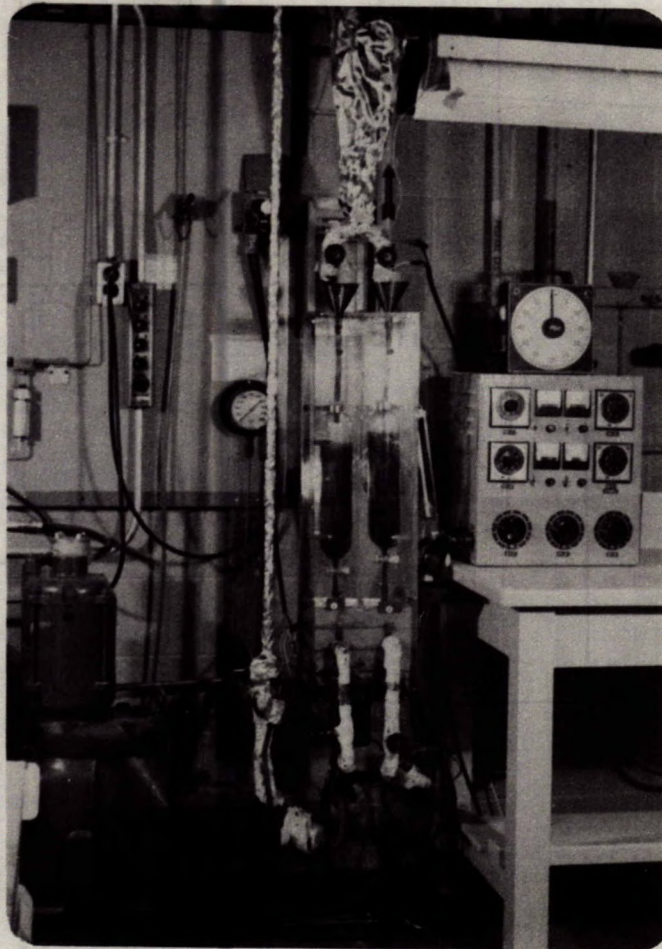


FIG 2. Front view of feed section for simulated aging test

Although it would be difficult, because of complexity of the reactions, to predict accurately the impact of changes of any processing condition, some overall effects can be derived from the fundamentals of reaction kinetics. The rate of individual reaction steps varies with temperature and concentration of reactants. Cracking reactions are endothermic and accelerate with increasing temperature, whereas hydrogenation reactions accelerate with increasing hydrogen pressure. Coke formation depends on the rates of cracking and dehydrogenation, and would therefore accelerate with increasing temperature and decreasing hydrogen pressure.

The conditions for "simulated aging" were chosen by performing a series of screening experiments to investigate the effect of variations in space velocity and temperature. The effect of hydrogen pressure on catalyst aging was studied previously using a different experimental system (5). In the present study, the hydrogen pressure was maintained constant at 13.9 MPa for all tests, which is within the practical range for hydrocracking. A satisfactory effect could not have been achieved by varying only space velocity; an increase in temperature was also necessary to reduce aging time sufficiently. After some preliminary experimentation, optimum deactivation conditions were found to prevail with a space velocity of 5 h^{-1} and at a temperature of 495°C .

The following series of tests under different operating conditions are documented in the present report:

- Series 1. True or base deactivation rates were measured at 450°C and at a liquid volumetric space velocity of 1 h^{-1} based on the reactor volume packed with the catalyst pellets. The corresponding feed rate was $152 \text{ mL}\cdot\text{h}^{-1}$ as no insert was placed in the reactor. The hydrogen flow rate was maintained at $35.6 \text{ cm}^3 \text{ s}^{-1}$ at STP. This test is referred to as true aging and was run continuously for 56 hours, and then periodically in five- to eight-hour intervals, totaling about 200 hours in all. Analyses were performed on samples of the liquid product accumulated in two to five hours of operation.
- Series 2. High space velocity tests were performed under the same conditions as for true aging - 13.9 MPa, 450°C , and without insert - except for a different arrangement of space velocities. Catalyst aging was carried out in two 12-hour periods during which space

velocity was maintained at 5 h^{-1} , and the hydrogen flow at $95 \text{ cm}^3 \text{ s}^{-1}$ at STP. The level of activity, initially and after each 12-hour period was determined by changing the space velocity to 1 h^{-1} , the hydrogen flow to $35.6 \text{ cm}^3 \text{ s}^{-1}$ at STP for two hours and analyzing the liquid sample that accumulated during these two hours.

Series 3. Simulated deactivation rates were measured at high temperature and high space velocity. This test series was run at 495°C and a liquid volumetric space velocity of 5 h^{-1} . The insert was placed in the reactor and the corresponding feed rate was $181 \text{ mL} \cdot \text{h}^{-1}$. The hydrogen flow rate was maintained at about $70 \text{ cm}^3 \text{ s}^{-1}$ at STP. The series was referred to as simulated aging and was run continuously for 32 hours. The liquid product that accumulated during each hour of operation was withdrawn for analysis.

Series 4. A link between simulated aging and true aging was sought by additional tests in the following manner. The simulated aging conditions were applied for a period of time and were then changed to match the true aging conditions for approximately two hours during which two liquid samples were obtained. The run was then terminated, the reactor re-loaded with a fresh catalyst, and the test was repeated for a different time period under simulated aging conditions. Three different time periods - 2, 4 and 6 hours, respectively - under simulated aging conditions were examined. No insert was placed in the reactor and the simulated aging test was run at 495°C with the feed rate of $760 \text{ mL} \cdot \text{h}^{-1}$, space velocity of 5 h^{-1} , and the hydrogen flow rate at $70 \text{ cm}^3 \text{ s}^{-1}$ at STP.

Several processing conditions were applied differently in each series of tests. For instance, in Series 2, the space velocity was five times greater than in Series 1, whereas the gas flow rate was only about three times greater. In Series 1, the gas flow:feed ratio was lower than in Series 3, but higher than in the simulated aging in Series 4. In addition, the length:diameter ratio was increased in Series 3 by placing the insert in the reactor, thereby increasing the linear velocity:space velocity ratio through the catalyst bed. The use of the insert and varying flow regime resulted from experience with the experimental system and facilitated smooth operation. The changes made were

necessary to prevent the reactor plugging and to maintain temperature profiles within the catalyst bed.

The impact of increasing temperature and space velocity is discussed in the next section of this report. Variations in hydrogen flow are not considered significant for the purpose of this investigation, because an excess of hydrogen was used in all experiments and because hydrogen flow seemed to exhibit only a small effect on product formation (6).

RESULTS AND DISCUSSION

True Aging

The results of the true aging tests are presented in Table 2. The deactivation pattern is shown in Fig. 3 in terms of an increase in the specific gravity of the liquid product and an increase in its sulphur content. It can be predicted by extrapolation that further deactivation would be recorded beyond 200 hours of operation. However, it can be seen that deactivation is more rapid in the early stages of the test than in the later stages. Since deactivation decelerates with time, the curves in Fig. 3 may eventually level off, indicating a constant activity. The decelerating deactivation is in agreement with results of a previous study which also showed that this leveling-off is relatively more pronounced and takes place earlier with increasing hydrogen pressure (5). Whether a state of constant activity in fact exists is not known as the patterns in Fig. 3 cannot be extrapolated with any precision. Furthermore, tests carried out continuously far longer than 200 hours of operation are necessary to determine deactivation patterns that are unaffected by start-up and shut-down procedures. These long-term tests are to be performed on a special testing system presently under construction.

High Space Velocity

The results of the high space velocity tests are shown in Table 3, which includes analytical data on liquid product samples obtained for both high and base space velocities of this series. The results for the base space velocities served as a measure of deactivation after completing a period with high space velocity. The deactivation is indicated in the left-hand side of Fig. 3.

TABLE 2
True Aging Run
Liquid Product Specifications

Time on stream (h)	Specific gravity (15/15°C)	S content (Wt %)	N content (Wt %)	H:C (atomic ratio)	Pitch (+525°C) content (Wt %)
3	0.891	0.29	0.15	1.664	7.7
5	0.889	0.35	0.16	1.662	
7	0.893	0.52	0.16	1.667	
9	0.895	0.49	0.17	1.661	
11	0.894	0.60	0.17	1.664	
13	0.905	0.78	0.21	1.645	12.9
16	0.910	0.64	0.22	1.643	
18	0.899	0.68	0.21	1.652	
20	0.909	0.87	0.17	1.636	
22	0.907	0.91	0.19	1.641	
25	0.911	0.94	0.20	1.641	11.5
27	0.903	0.78	0.20	1.651	
29	0.915	1.03	0.21	1.638	
31	0.908	0.87	0.21	1.633	
33	0.909	0.91	0.22	1.632	
36	0.908	0.78	0.21	1.641	13.6
38	0.919	0.90			
40	0.911	0.86			
42	0.918	0.96			
45	0.910	0.81			
47	0.920	1.16			15.1
49	0.912	1.02			
51	0.912	1.03			
54	0.913	1.07			
56	0.914	1.08			
59	0.913	1.18	0.24	1.600	
61	0.916	1.15			
64	0.914	1.18			
66	0.917	1.21			
68	0.918	1.23			
70	0.919	1.23			16.6
72	0.914	1.14			
74	0.917	1.14			
77	0.917	1.31			
79	0.926	1.40			
84	0.914	1.32	0.28	1.602	
89	0.911	1.23			
95	0.915	1.23			
100	0.917	1.30			
105	0.916	1.21			
110	0.921	1.41			16.0
115	0.916	1.40			
120	0.920	1.47			
125	0.914	1.35			
130	0.921	1.52			
135	0.924	1.61	0.29	1.590	
140	0.924	1.62			
145	0.925	1.67			
150	0.922	1.60			
155	0.926	1.68			
160	0.928	1.78			16.0
165	0.925	1.64			
170	0.928	1.68			
175	0.924	1.71			
180	0.928	1.72			
185	0.927	1.69			16.0
190	0.929	1.75			
195	0.929	1.77			

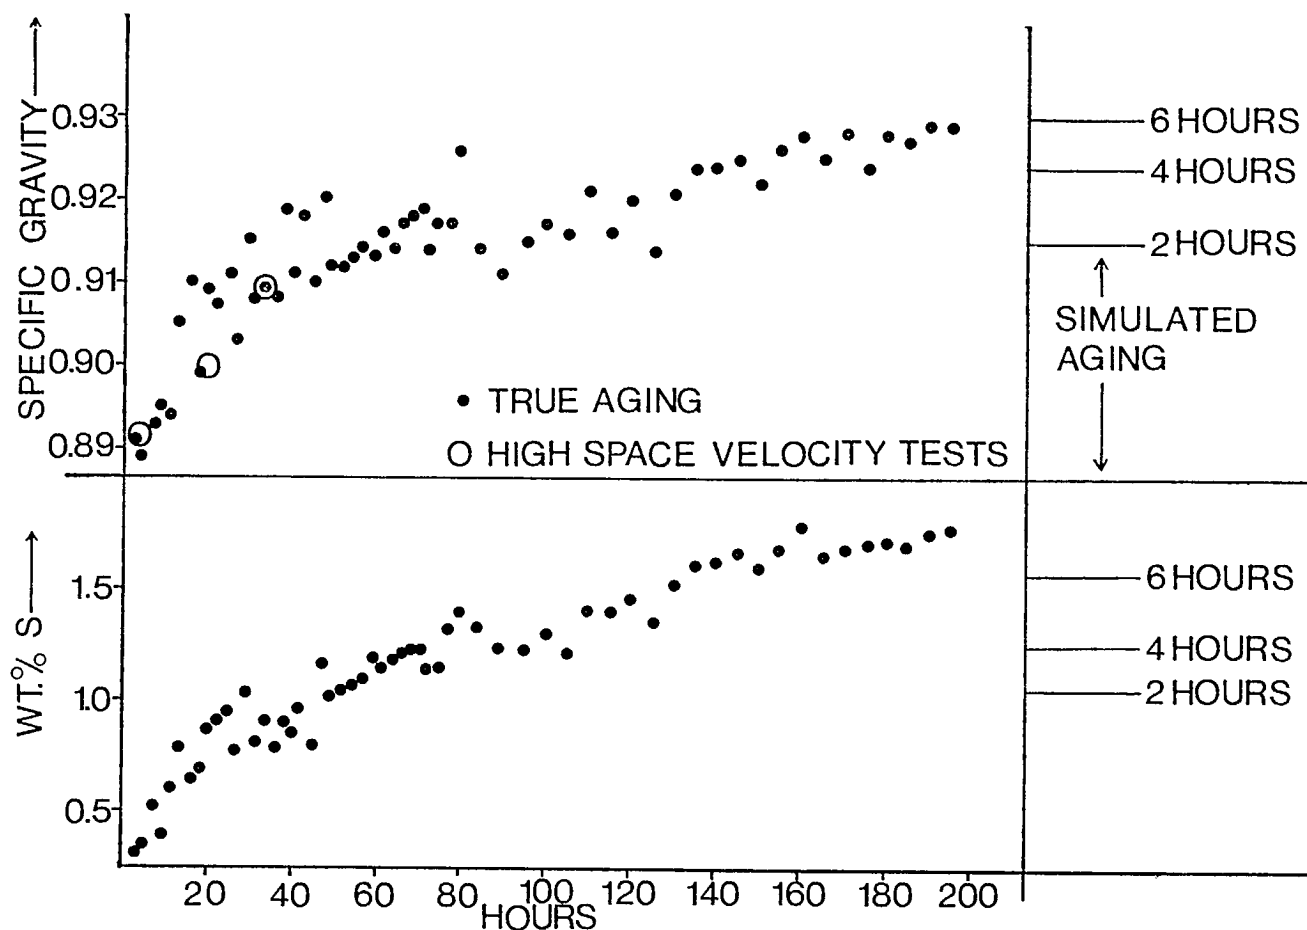


Fig. 3. Specific gravity (15/15°C) and sulphur content (wt %) in the liquid product versus time on stream (h) during true aging. O indicates high space velocity experiments. Activity levels on right-hand side relate to different time periods under simulated aging.

TABLE 3

High Space Velocity Run
Liquid Product Specifications

Time on stream (h)	Specific gravity (15/15°C)	S content (Wt %)	N content (Wt %)	H:C (atomic ratio)	Pitch (+525°C) content (Wt %)	Space velocity (h ⁻¹)
4	0.892	0.60	0.12	1.630	3.5	1
7	0.959	2.54				5
10	0.962	2.60				5
15	0.962	2.58				5
20	0.900	0.70	0.16	1.621	8.7	1
24	0.964	2.70				5
32	0.968	2.85				5
34	0.909	1.12	0.19	1.607	12.9	1

A five-fold increase in feed rate had an insignificant effect on the rate of deactivation. One could rationalize this finding by assuming that lower conversions caused by reduced residence time would compensate for the greater feed rate in relation to coke formation. However, a more detailed analysis would reveal that the relationship between the space velocity and the rate of deactivation may be more complex, mainly because of the multicomponent structure of the reaction system. The concentration of reaction constituents depends on the rates of their formation and depletion. Thus the total yield of a component may not be a monotonic function of the residence time. If some coke precursors react faster than others, then their participation in total coke formation depends on the space velocity, a change in which may consequently be reflected in both the quantity and the quality of the coke deposits. For example, a coke-forming reaction is fast enough to be completed in a time interval shorter than the contact time with the catalyst bed. On increasing the space velocity, this reaction would then yield more coke, since more molecules would have a chance to undergo the reaction.

In addition to chemical phenomena, mechanical regeneration may take place whereby particles of coke are detached from the surface by abrasion or by dissolution of the binding carbonaceous material. Although evidence for this regeneration is not available, an effective regeneration caused by washing with a refinery solvent was documented previously (7). Should a similar process take place while bitumen is used, it would be enhanced by increasing the space velocity.

The high space velocity series indicated that the desired effect could not be established by changing the space velocity at base temperature. To accelerate aging substantially, the catalyst fouling was simulated at a higher reaction temperature. The term simulated aging is used to emphasize the severe consequences of the change in temperature.

Simulated Aging

The results of the simulated aging tests are given in Table 4 and the deactivation patterns are shown in Fig. 4. The activity dropped rapidly in the first period of the run, leveled off, and remained approximately constant beyond 15 hours of operation.

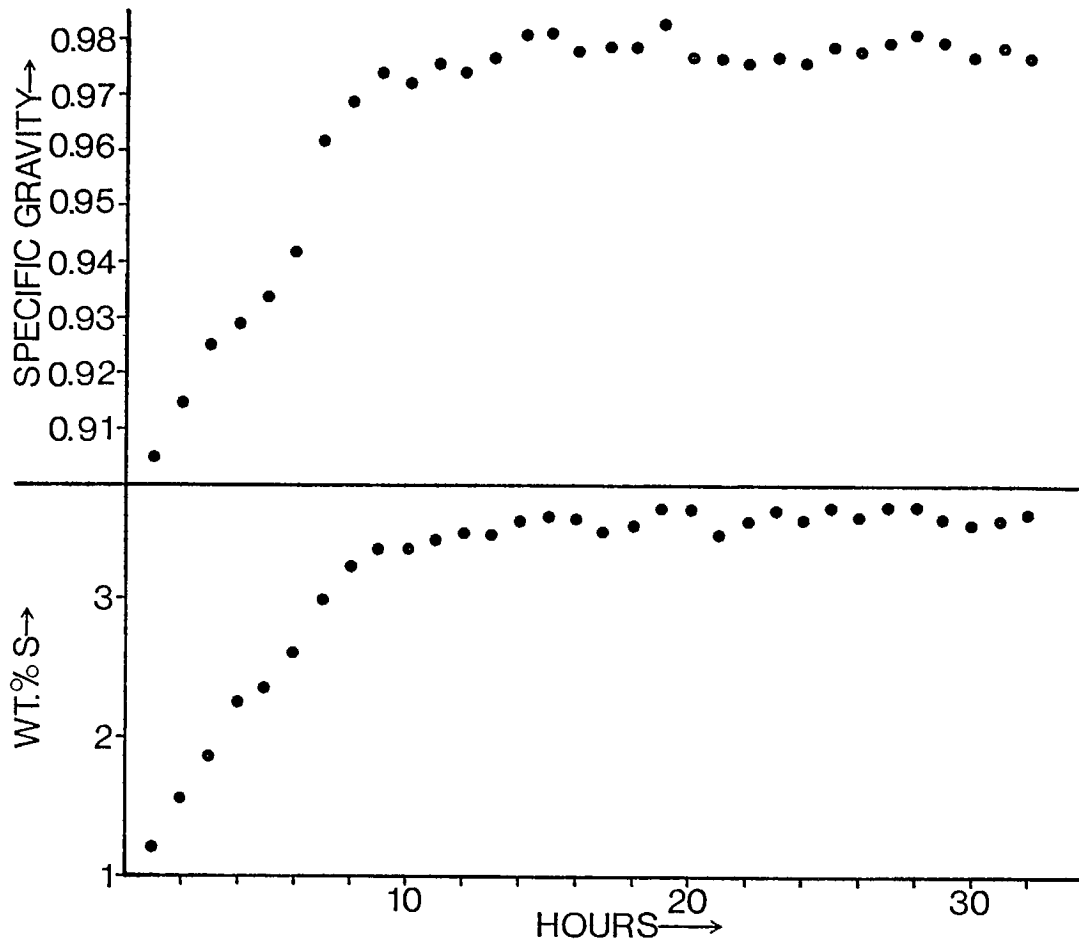


Fig. 4. Specific gravity (15/15°C) and sulphur content (wt %) in the liquid product versus time on stream (h) during simulated aging

As mentioned earlier, the cracking reactions and coke formation were expected to accelerate with increasing temperature. It is noteworthy to compare the initial performance under simulated aging with that of true aging. Table 4 shows that the initial pitch conversion was relatively high. The initial specific gravity and nitrogen content in Table 4 could be compared with true aging levels after approximately 30 hours of operation. As shown in Table 4 the initial sulphur content compared with true aging levels after about 70 hours of operation (Fig. 3). The hydrogen:carbon ratio in the liquid product was substantially lower under simulated aging conditions. This ratio corresponded to that under true aging conditions after about 200 hours of operation.

The performance under simulated aging reflected the effect of both high temperature and high space velocity. The performance seemed to be more sensitive to temperature, particularly with respect to the pitch fraction of the bitumen. The initial high pitch conversion observed could result from molecular weight reduction or growth. Molecular growth would result in precipitation of coke, most of which would be retained on the catalyst surface and reactor walls. The molecular weight reduction by cracking would generate compounds having a lower boiling point than those contained in the pitch. It is apparent that, whereas both of the latter processes have taken place simultaneously, the growth rate was much smaller because the amount of coke formed accounts for only a fraction of the pitch converted. However, the high temperature of simulated aging compared with true aging shifted the balance towards coke formation as reflected in rapid catalyst deactivation.

Less extensive hydrogenation under simulated aging conditions, indicated by a low H:C ratio, was presumably due to a high aromatic carbon content. An analysis by Fourier Transform C-13 N.M.R. indicated that the unsaturated carbon represented about 30% of the total carbon in the initial product of simulated aging compared with about 20% of that of true aging. The following reasons may be considered to account for changes in the aromatic carbon content. More extensive splitting of side chains from aromatic rings caused by the higher temperature could have yielded more gas in the product. Apart from hydrocracking reactions, the higher temperature also shifts the naphthenes-aromatics equilibria towards formation of aromatics (8). In addition to the temperature effects, the high space velocity of simulated aging may have hindered the extent of hydrogenation because of the shorter contact time.

TABLE 4
Simulated Aging Run
Liquid Product Specifications

Time on stream (h)	Specific gravity (15/15°C)	S content (Wt %)	N content (Wt %)	H:C (atomic ratio)	Pitch (+525°C) content (Wt %)
1	0.905	1.21	0.22	1.582	0
2	0.915	1.56	0.27	1.559	0
3	0.925	1.85	0.30	1.543	3.1
4	0.929	2.24	0.30	1.552	3.3
5	0.934	2.36	0.30	1.547	4.7
6	0.942	2.61	0.32	1.533	
7	0.962	2.99	0.35	1.513	12.6
8	0.969	3.21	0.36	1.480	17.7
9	0.974	3.35	0.40	1.479	22.9
10	0.972	3.35	0.39	1.489	22.9
11	0.976	3.40	0.38	1.487	26.7
12	0.974	3.45	0.37	1.496	
13	0.977	3.44	0.39	1.491	
14	0.981	3.54	0.38	1.490	
15	0.981	3.57	0.38	1.492	
16	0.978	3.55		1.484	
17	0.979	3.47	0.39		
18	0.979	3.51		1.486	28.7
19	0.983	3.63	0.39		
20	0.977	3.62		1.488	
21	0.977	3.44	0.40		
22	0.976	3.54		1.484	
23	0.977	3.62	0.39		
24	0.976	3.55		1.464	
25	0.979	3.64	0.39		
26	0.978	3.57		1.479	
27	0.980	3.65	0.40		
28	0.981	3.64		1.477	
29	0.980	3.55	0.40		
30	0.977	3.52		1.464	24.7
31	0.979	3.55	0.39		
32	0.977	3.59		1.464	

TABLE 5
Deactivation Levels for Simulated Aging
Liquid Product Specifications

Time on stream (h)	Specific gravity (15/15°C)	S content (Wt %)
2	0.915	1.06
4	0.924	1.26
6	0.930	1.57

The sulphur and nitrogen contents in the liquid product from simulated aging were affected by both high temperature and high space velocity as an increase in temperature alone would result in more desulphurization and denitrogenation of the liquid product. The reasons why desulphurization was initially more severely reduced than denitrogenation under simulated aging conditions are not known. It is possible that more nitrogen-containing molecules were eliminated by being involved in coke formation. Changes in relative contributions of bitumen constituents to coke formation are expected to take place with changing processing conditions (9).

Link between Simulated and True Aging

Since the rate of deactivation under simulated aging conditions could not easily be related to the rate of deactivation under true aging conditions, a series of experiments was performed in which a link was sought between simulated and true aging. The purpose of these experiments was to measure the level of activity under true aging conditions after the catalyst had been subjected to simulated aging conditions for a certain period of time, and then to graphically estimate the time in which the catalyst would deteriorate enough to reach this level of activity while being subjected to true aging conditions.

The results of this series of experiments are shown in Table 5 and the activity levels determined for three different time periods under simulated aging are marked on the right-hand side of the curves in Fig. 3. By applying these results it was estimated that 2 hours of operation under simulated aging conditions would correspond to about 50-70 hours under true aging, and similarly, 4 hours to 100-150 hours, and 6 hours to 150-200 hours. Hence, assuming that simulated aging is approximately 30 times faster than true aging, one could extrapolate the pattern of true aging and speculate that it would level off in about 400 hours of operation.

Estimating the link between true and simulated aging in Fig. 3 is an approximation only. However, it is apparent that by using simulated aging conditions, the deactivation was accelerated sufficiently to proceed substantially in a very short time. It is expected that by applying this method to a number of catalysts, preliminary information can be obtained by

comparing their deactivation patterns such as the one shown in Fig. 4. This information would then be available either in addition to the true aging data, or for use with catalysts on which true aging tests are not warranted.

CONCLUSIONS

A technique that simulates catalyst aging was devised. The purpose in applying this technique was to compare aging data which could be provided in a much shorter time than is normally required. The objective of establishing rapid deactivation was met and an experimental relationship indicated that simulated aging progresses about thirty times faster than actual aging.

ACKNOWLEDGEMENTS

The authors wish to express their sincere appreciation to R.W. Taylor for modifying the experimental system and to L. Galbraith for technical assistance.

REFERENCES

1. McColgan, E.C. and Parsons, B.I. "The hydrocracking of residual oils and tars. Part 6: Catalyst deactivation by coke and metals deposition"; Department of Energy, Mines and Resources, Mines Branch [since renamed Canada Centre for Mineral and Energy Technology (CANMET)] Research Report R273; 1974.
2. Ranganathan, R., Pruden, B.B., Ternan, M. and Denis, J.M. "Evaluation of a two-stage thermal and catalytic hydrocracking process for Athabasca bitumen"; Energy Mines and Resources, Canada, CANMET Report 77-37; 1977.
3. Ternan, M. and Parsons, B.I. "Finely divided coke or coal as a catalyst support for the catalytic hydrocracking of heavy crude oils and bitumen"; CANMET Lab Report ERP/ERL 77-109 (TR); 1977.
4. O'Grady, M.A. and Parsons, B.I. "The hydrogenation of Alberta bitumen over cobalt molybdate catalyst"; Department of Energy, Mines and Resources, Mines Branch, Research Report R194; 1967.
5. Ranganathan, R., Logie, R.B. and Denis, J.M. "Catalytic hydrocracking of Athabasca bitumen in a fluidized bed reactor - effect of pressure on catalyst decay"; Energy, Mines and Resources, Canada, CANMET Report 77-40; 1976.
6. Merrill, W.H., Logie, R.B. and Denis, J.M. "The effect of hydrogen recycle rate on the non-catalytic hydrocracking of G.C.O.S. separated bitumen"; Department of Energy, Mines and Resources, Mines Branch; Divisional Report FRC 72/115-PPE; 1972.
7. Kriz, J.F. Unpublished results.
8. Gully, A.J. and Ballard, W.P. "Hydrogenation of catalytic cracking charge stocks"; Adv Pet Chem Refin (New York, Interscience, Publishers) 7:240-282; 1963.
9. Lipovich, V.G., El'bert, E.I., Lur'e, M.A., Krestovnikova, L.R., Vetlugina, L.N. and Kalechits, I.V. "Relative contributions of hydrocarbons to formation of carbonaceous deposits on alumina/molybdenum and alumina/cobalt/molybdenum catalysts"; Int Chem Eng 18:1:98-99; 1978.

CANMET REPORTS

Recent CANMET reports presently available or soon to be released through Printing and Publishing, Supply and Services, Canada (addresses on inside front cover), or from CANMET Publications Office, 555 Booth Street, Ottawa, Ontario K1A 0G1:

Les récents rapports de CANMET, qui sont présentement disponibles ou qui ce seront bientôt peuvent être obtenus de la direction de l'Imprimerie et de l'Édition, Approvisionnement et Services, Canada (adresses au verso de la page couverture), ou du Bureau de Vente et distribution de CANMET, 555 rue Booth, Ottawa, Ontario, K1A 0G1:

- 7B-2 Revision of recommended values for reference ores MP-1 and KC-1; G.H. Faye and W.S. Bowman;
Cat. No. M38-13/78-2, ISBN 0-660-01712-1; Price: \$1.00 Canada, \$1.20 other countries.
- 78-3 Certified and provisional reference materials available from the Canada Centre for Mineral and Energy Technology, 1978; G. Faye;
Cat. No. M38-13/78-3, ISBN 0-660-01804-7; Price: \$1.25 Canada, \$1.50 other countries.
- 78-5 Certification of reference iron ore SCH-1 for sodium and potassium; R. Sutarno, D.J. Charette, W.S. Bowman and G.H. Faye;
Cat. No. M38-13/78-5, ISBN 0-660-01808-X; Price: \$1.00 Canada, \$1.20 other countries.
- 78-6 Catalogue of CANMET publications - Catalogue des publications de CANMET 1976/77; C. Mamen, Editor;
Cat. No. M38-13/78-6, ISBN 0-660-01849-7; Price: \$4.00 Canada, \$4.80 other countries.
- 78-8 Preparation of a ceramic electrolyte in the system $MgO-K_2O-TiO_2$; H.H. Quon and T.A. Wheat;
Cat. No. M38-13/78-8, ISBN 0-660-10006-1; Price: \$3.00 Canada, \$3.60 other countries.
- 78-9 Design guidelines for multi-seam mining at Elliot Lake; D.G.F. Hedley;
Cat. No. M38-13/78-9, ISBN 0-660-10047-9; Price: \$1.25 Canada, \$1.50 other countries.
- 78-10 Block flow slope stability; D.F. Coates and Y.S. Yu;
Cat. No. M38-13/78-10, ISBN 0-660-10019-3; Price: \$1.00 Canada, \$1.20 other countries.
- 78-11 Equipment and procedures to determine ground stresses in a single drill hole; G. Herget, P. Miles and W. Zawadsky;
Cat. No. M38-13/78-11, ISBN 0-660-10007-X; Price: \$1.25 Canada, \$1.50 other countries.
- 78-14 The mineral sources of silver and their distribution in the Caribou massive sulphide deposit, Bathurst area, New Brunswick; J.L. Jambor and J.H.G. Laflamme;
Cat. No. M38-13/78-14, ISBN 0-660-10105-X; Price: \$1.00 Canada, \$1.20 other countries.
- 78-15 Performance of high alumina cement concrete stored in water and dry heat at 25, 35 and 50°C; D.H.H. Quon and V.M. Malhotra;
Cat. No. M38-13/78-15, ISBN 0-660-10037-1; Price: \$2.50 Canada, \$3.00 other countries.
- 76-40F Evaluation des charbons marchands canadiens: Nouvelle-Ecosse et Nouveau Brunswick - 1975; T.E. Tibbetts et W.J. Montgomery;
Cat. No. M38-13/76-40F, ISBN 0-660-01821-7; Price: \$3.00 Canada, \$3.60 other countries.
- 76-22F Manuel sur la pente des mines à ciel ouvert - Chapitre 1 - Sommaire; R. Sage;
Cat. No. M38-14/1-1978F, ISBN 0-660-90030-0; Price: \$2.50 Canada, \$3.00 other countries.
- 77-55F Ressources canadiennes en rebuts minéraux rapport n° 2 - Les rebuts minéraux au Québec; R.K. Collings;
Cat. No. M38-13/77-55F, ISBN 0-660-90019-X; Price: \$1.75 Canada, \$2.10 other countries.